Proceeding for ISS2000

arXiv:cond-mat/0010340v1 [cond-mat.supr-con] 23 Oct 2000

Neutron scattering studies of Zn-doped $La_{2-x}Sr_xCuO_4$

K. Hirota
Department of Physics, Tohoku University, Sendai 980-8578, Japan

(February 1, 2008)

This paper reviews studies of the spatial modulation of spin in $La_{2-x}Sr_xCuO_4$ (LSCO) through neutron-scattering measurements of the *elastic* magnetic peaks, with emphasis on Zn-doped LSCO. The elastic incommensurate magnetic peaks can be categorized in two classes with respect to the temperature dependence. Nd-doped LSCO, La_2CuO_{4+y} and LSCO with $x \sim 1/8$ exhibit an ordinary power law behavior. On the other hand, Zn-doped LSCO and LSCO with $x = 0.02 - 0.07$ show an exponential temperature dependence, and the correlation lengths stay short. This discrepancy can be attributed to the difference in the mechanism of pinning spin fluctuations. The former systems have pinning centers which is *coherent* to the lattice. In the latter, however, pinning centers are randomly scattered in the CuO_2 planes, thus *incoherent*. The incoherent pinning model is discussed with referring to recent μSR studies.

Keywords: $La_{2-x}Sr_xCuO_4$, Neutron scattering, Elastic magnetic peaks, Zn substitution

I. INTRODUCTION

Interrelation between superconductivity and magnetism has been a central issue in the research of high T_c superconductivity for many years [1]. In particular, $La_{2-x}Sr_xCuO_4$ (LSCO) has been extensively studied by neutron scattering, because LSCO has the simplest crystal structure among high-T_c superconductors. The following things had been clarified by mid 1990's: (1) The mother compound La_2CuO_4 is three-dimensional antiferromagnetic (AF) insulator [2]. (2) The AF ordering is destroyed by a slight hole doping ($x \sim 0.02$), and the spin glass (SG) phase appears, in which commensurate two-dimensional (2D) short-range AF fluctuations are observed. [3,4] (3) The superconductivity is realized in a certain hole concentration range ($0.05 < x < 0.27$), and T_c becomes maximum around $x = 0.15$ [4–6]. (4) Inelastic magnetic peaks appear at four *incommensurate* positions equivalent to $\mathbf{Q}_\delta = (\pi, \pi) + \delta(\pi, 0)$ of the CuO_2 square unit in the superconducting range [7]: Yamada *et al.* [8] have shown that the incommensurability δ follows a simple empirical relation $\delta = x$, then saturates around $\delta \sim 1/8$ beyond $x \sim 1/8$.

The inelastic incommensurate magnetic peaks in LSCO have been theoretically understood in the framework of the *t*-*J* model as nesting of the Fermi surface [9,10]. However, this view is recently challenged by a real-space domain picture, i.e., the stripe model [11,12]. Tranquada *et al.* [11] have found evidence for a static ordering of AF stripes separated by charged domain walls with an incommensurate modulation in $La_{1.6-x}Nd_{0.4}Sr_xCuO_4$ (LNSCO) samples with $x = 0.12$, 0.15 and 0.20. They found that the *elastic* magnetic peaks appear with the incommensurability consistent with that of the dynamic spin fluctuations in LSCO without Nd doping, and that the correlation lengths reaches ~ 200 Å for $x = 0.12$. They have also found an structural evidence for charge ordering. T_c's are reduced with respect to those in the absence of Nd doping, which is believed to have the same origin as that in $La_{2-x}Ba_xCuO_4$ near $x = 1/8$ [13,14] because both systems show a transition to low temperature tetragonal (LTT) phase below ~ 70 K in contrast with LSCO which retains the low temperature orthorhombic (LTO) structure to the lowest temperature measured. Tranquada *et al.* [11] speculated that the LTT phase is essential for the static stripe order, which competes with the superconductivity.

The coincidence between the elastic and inelastic magnetic peak positions has led to reconsideration of static and dynamic spatial structures of spin in high T_c superconductors, particularly from the point of view of the stripe model. In this paper, review is given of the results of a wide variety of neutron-scattering studies on the elastic incommensurate magnetic peaks in Sec. II. Several important features concerning spatial structures of spin are summarized in Sec. III. We then categorize the elastic magnetic peaks into two classes with respect to the pinning mechanism of AF fluctuations, namely, coherent and incoherent pinning.

II. OVERVIEW OF THE ELASTIC MAGNETIC PEAKS IN LSCO

It was a fundamental issue whether the static magnetic order found in LNSCO is its characteristic feature or somewhat universal to high-T_c superconductors. It is known that T_c is suppressed by Zn substitution for Cu, and also in LSCO with $x \sim 1/8$. Goto *et al.* [15] have studied LSCO with $x = 0.115$ by NMR and concluded that magnetic order appears even in the absence of the LTT structure. Kumagai *et al.* [16] have clarified by μSR measurements that there exists a static magnetic field in LSCO, which onset temperature reaches maximum at $x \sim 0.12$. Since the magnetic ordering seems more stable with lower T_c samples in LNSCO, it was natural to start looking for elastic magnetic signals in Zn-doped LSCO and LSCO with $x \sim 1/8$.

Hirota *et al.* [17] have observed quasielastic magnetic peaks, with the correlation length of $\sim$ 80 Å in $La_{2-x}Sr_xCu_{1-y}Zn_yO_4$ (LSCZO) with $x = 0.14$ and $y = 0.012$ ($T_c = 19$ K). As shown in Fig. 1, the quasielastic component starts increasing below $T_m \sim 20$ K, while the low-energy inelastic response appears at the same δ with a broad intensity maximum around T_m. These findings indicate that small Zn doping induces quasistatic AF ordering at low temperature by shifting the spectral weight from inelastic region. These results mirrored the behaviors seen in samples in the SG region [3,4]

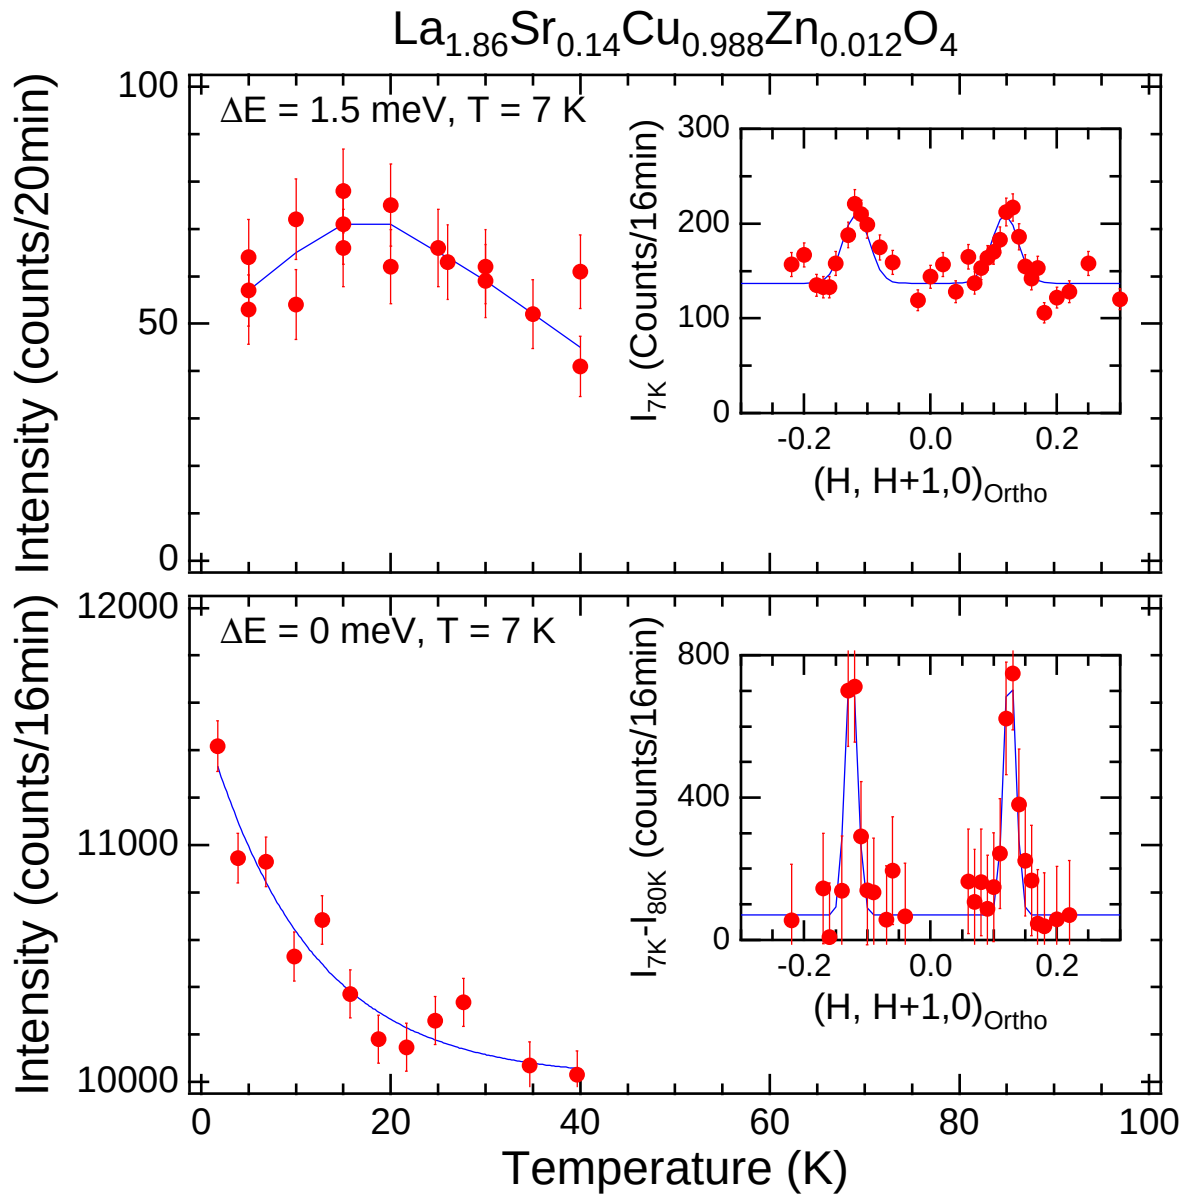

FIG. 1. Temperature dependence of the incommensurate magnetic peaks at 0 and 1.5 meV transfer for $La_{1.86}Sr_{0.14}Cu_{0.988}Zn_{0.012}O_4$ ($T_c = 19$ K). Each inset shows a peak profile along orthorhombic (q $1+q$ 0) at 7 K. From Hirota *et al.* [17].

Suzuki *et al.* [18] have obtained evidence for incommensurate magnetic order at low temperature in LSCO with $x = 0.12$ by using a double-axis neutron diffractometer. Detailed elastic neutron-scattering measurements were carried out by Kimura *et al.* [19,20]. They have found *elastic* incommensurate magnetic peaks indicating a spin-density wave (SDW) order with correlation length exceeding 200 Å. The magnetic peaks start appearing below $T_m \sim 30$ K, which coincides with onset $T_c = 31$ K. Subsequent studies by Matsushita *et al.* [21] on LSCO with $x = 0.10$ and 0.13 have revealed that T_m rapidly decreases and differs from T_c, and that the correlation lengths also drastically diminishes. For the $x = 0.15$ and 0.18 samples, Yamada *et al.* [8] had already confirmed that there exists no elastic magnetic scattering and that only inelastic incommensurate scattering remains with an energy gap of $\sim$ 4 meV at low temperature.

These discoveries are important not only because the incommensurate SDW order is confirmed in the absence of LTT, but also because they have urged efforts to understand the spatial structure of spin in further detail than that accomplished in inelastic neutron-scattering studies. Lee *et al.* [22] have found a long-range SDW order in the superconducting state of a predominantly stage-4 $La_2CuO_{4.12}$ ($T_c = 42$ K). They have found that the elastic magnetic peaks appear at the same temperature within the errors as the superconductivity, suggesting that the two phenomena are strongly correlated. Even more importantly, as shown in Fig. 2(a), their detailed measurements have revealed that the elastic magnetic peaks are not located at 4-fold symmetrical position around (π, π), i.e., corners of a square, but form a rectangular which has 2-fold symmetry around the orthorhombic [1 0 0] axis. This indicates that the direction of the spin modulation is rotated from perfect alignment along the Cu-O-Cu direction by a finite angle θ_Y, which is 3.3° for $La_2CuO_{4.12}$. The shift of SDW peaks, or the Y shift, implies that the magnetic correlations have one-dimensional anisotropy on the 2D CuO_2 plane. The Y shift was also confirmed in LSCO $x = 0.12$ [20].

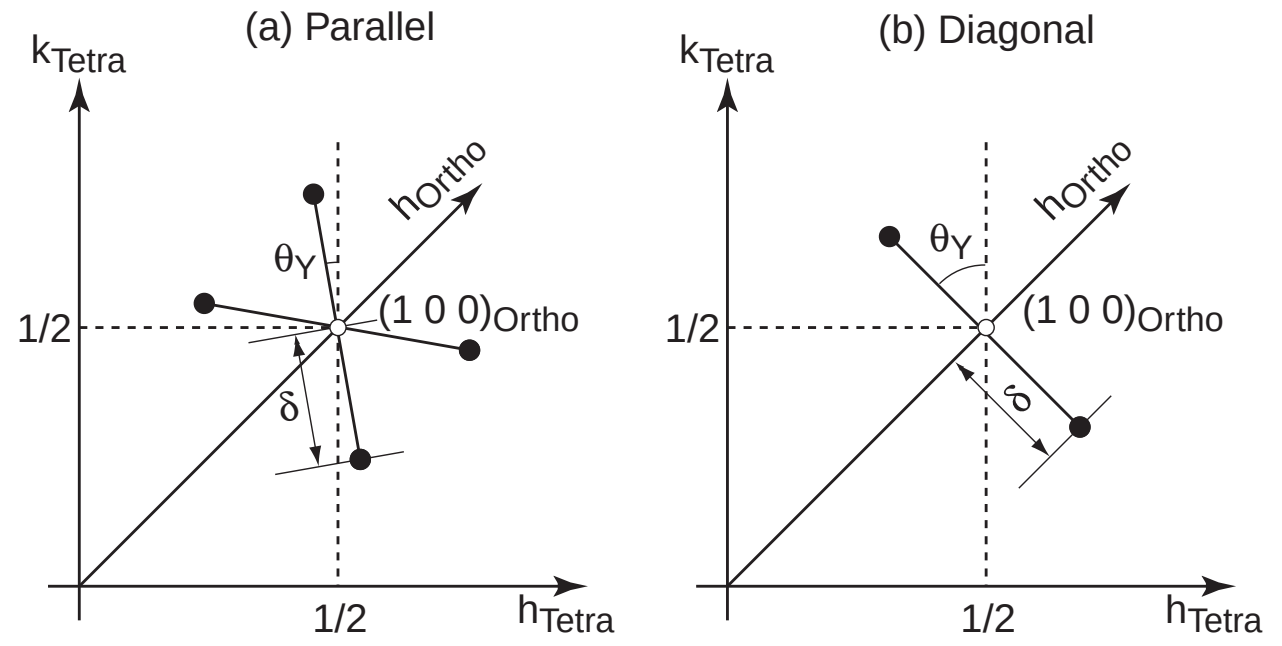

FIG. 2. Schematic diagram of the incommensurate positions of magnetic peaks (a) parallel and (b) diagonal to the Cu-O-Cu direction. Note that the angle θ_Y is defined as a rotation from the tetragonal [0 1 0] direction.

The magnetic scattering in the SG phase of LSCO ($0.02 \leq x \leq 0.05$) was also revisited. One of the most important findings was done by Wakimoto *et al.* [23], who have discovered new satellite magnetic peaks in LSCO $x = 0.05$ at positions rotated by $\sim 45°$ in reciprocal space about (π, π) from those found in the superconducting phase ($x \geq 0.06$). Due to twinning in LSCO single crystals, the orthorhombic (1 0 0) and (0 1 0) positions nearly coincide with each other at (π, π). Wakimoto *et al.* have employed a narrower instrumental Q resolution and succeeded in ascribing a certain magnetic peak to a certain twin; in a single twin, there exist only two satellites with the modulation vector along the orthorhombic b^* axis as shown in Fig. 2(b) [24]. These works indicate that the SDW modulation is diagonal to the Cu-O-Cu axis for the $x = 0.05$ insulating sample, and suddenly turns to be parallel to the direction upon crossing the insulator-to-superconductor phase boundary at $x_c \sim 0.055$. Subsequent studies by Fujita *et al.* [27] have revealed that the well-defined diagonal peaks in the insulating region suddenly broadens upon entering the superconducting phase and finite intensities appear at the parallel positions, which indicate an intimate relation between the parallel SDW modulation and the superconductivity. Lower hole concentration region has been studied by Matsuda *et al.* [28,29]. They have found that the diagonal SDW modulation occurs universally across the insulating SG phase down to $x = 0.02$.

III. SPATIAL STRUCTURES OF SPIN IN LSCO

Table I summarizes characteristic properties of elastic magnetic scattering observed in LSCO and related compounds to date. Several important features of the elastic magnetic peaks are listed as follows:

- The elastic peaks in the superconducting phase appears at nearly the same incommensurate position for the inelastic peaks. Shift of spectral weight from inelastic to elastic component with lowering temperature was observed in LSCZO [17].
- The elastic peaks in the superconducting phase exhibit a characteristic rotation, called Y shift [22] around (π, π).
- Transition from Parallel to Diagonal SDW coincides with the appearance of superconductivity at $x_c \sim 0.055$ [24,27].
- Incommensurability δ follows an empirical relation $\delta = x$ for $x \leq 1/8$, even below x_c. It deviates from the line below $x = 0.024$ [29].
- The correlation lengths ξ drastically shorten upon doping. ξ shows a large anisotropy in low x [28], but becomes isotropic with increasing x. ξ appears shortest near x_c [27].
- No significant anomaly is observed at x_c in the x dependence of the magnetic moment μ [25] as observed for the orthorhombicity [27].
- ξ is exceptionally long in LSCO $x \sim 0.12$ [20], LNSCO [11], and La_2CuO_{4+y} [22].
- T_m seems enhanced where T_c is suppressed as seen in LSCO and LNSCO, which seems however not the case for La_2CuO_{4+y} [22].

The spatial spin structure on the CuO_2 plain is closely related to the superconductivity. However, the SDW order seems not completely universal in all LSCO and related compounds.

IV. COHERENCE OF PINNING

Let us examine the temperature dependence of the elastic magnetic peaks. As shown in Fig. 3, the order parameter exhibits an ordinary power-law behavior for $La_2CuO_{4.12}$ [22], but exponentially increases with decreasing temperature for LSCO with $x = 0.02$ [28]. As a matter of fact, all the elastic magnetic scattering peaks studied can be categorized into these two classes, power-law and exponential. LNSCO with $x = 0.12$ and $x = 0.15$ [11], LSCO with $x = 0.12$ [19] and La_2CuO_{4+y} show a power-law ordering, while LSCO with $x = 0.2 - 0.7$ [23] and Zn-doped LSCO [17,19] display a more like exponential curve. The magnetic moment in LNSCO with $x = 0.20$ is small and overwhelmed by Nd-ordering, thus the shape of the order parameter is not very clear.

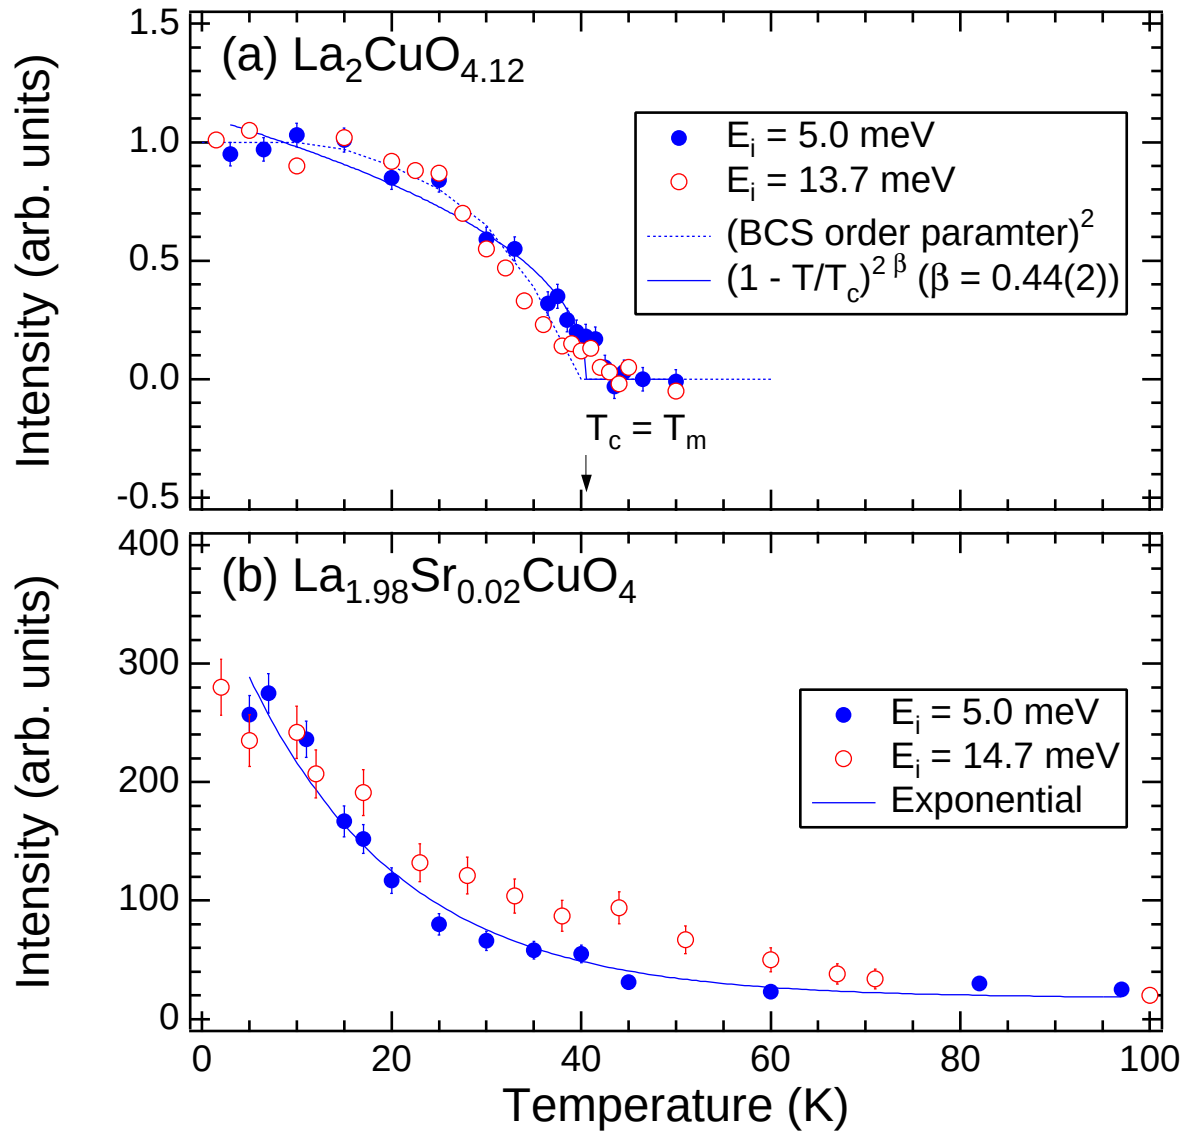

FIG. 3. (a) Temperature dependence of the peak intensity of the incommensurate elastic scattering of $La_2CuO_{4.12}$. Filled and open circles correspond to the incident energy E_i of 5.0 and 13.7 meV, yielding energy resolutions of 0.15 and 0.9 meV FWHM. From Lee *et al.* [22]. (b) Temperature dependence for LSCO with $x = 0.02$. Filled and open circles correspond to E_i of 5.0 and 14.7 meV, yielding 0.25 and 0.9 meV FWHM resolutions. From Matsuda *et al.* [28].

If the elastic magnetic component is derived from the inelastic components as mentioned, there should be some specific mechanisms condensing AF spin fluctuations. In the LTT structure, the tilt direction of the CuO_6 octahedra is along the Cu-O-Cu direction, i.e., tetragonal [1 0 0], which is ~ 45° rotated from [1 1 0] as in the LTO phase. Tranquada *et al.* [11] speculated that a coupling between the tilt modulation and the charge-stripe correlations is possible only when the tilts have a [1 0 0] orientation, which induces the SDW order at lower temperature. As for the charge-stripe order, their speculation concerning the necessity of LTT seems valid because no signature of the charge ordering has been reported for LTO systems. However, hole concentration near $x \sim 1/8$ and excess oxygens which show staging order in $\mathrm{La_2CuO_{4+y}}$ can also induce a long-range SDW order. A feature common to LTT, $x \sim 1/8$ and oxygen staging order is *coherence* to the lattice, though the coherence length may be shorter for $x \sim 1/8$ than for the others. They are pinning centers which periodicity is commensurate with the lattice, and may change the electronic and structural state of the $\mathrm{CuO_2}$ plane in a fairly long range. In these cases, the magnetic correlations can be developed to a true long-range order.

On the other hand, doped Zn ions and holes in low density are randomly distributed in the $\mathrm{CuO_2}$ plane, thus *incoherent* to the lattice. These pinning centers slow AF fluctuations locally and form local SDW domains. Considering the correlation length estimated for LSCZO with $x = 0.14$ and $y = 0.012$, $\xi \sim 80$ Å , one might realize that ξ is too long for each SDW domain around a Zn ion to be separated from the other domains because the average distance between nearest Zn ions is $\sqrt{a^2/y} \sim 35$ Å where a is the Cu-O-Cu distance and y is the doping rate of Zn. If magnetic order induced around Zn is static and has more or less similar spatial spin modulation, most of the domains are connected or *percolated* and result in a long-range order.

Nachumi *et al.* [31] have performed transverse-field μSR measurements of Zn-doped LSCO. They have estimated the superconducting carrier density/effective mass n_s/m^* ratio at low temperature, and found that n_s/m^* decreases with increasing Zn concentration. They have then proposed "swiss cheese" model where charge carriers within an area $\pi\xi^2_{\mu\mathrm{SR}}$ around each Zn are excluded from superconductivity. For LSCZO with $x = 0.15, y = 0.01$ and $x = 0.20, y = 0.01$, they have obtained $\xi_{\mu\mathrm{SR}} = 18.3$ Å. For the $x = 0.15, y = 0.01$ sample, weak static magnetic order was confirmed below 5 K.

Their "swiss cheese" model seems relevant to our local and incoherent SDW domain picture, though the characteristic lengths are quite different. One of the major difference between μSR and neutron scattering is their time scale. "Elastic" means fluctuations slower than 10^{11}Hz (0.4 meV) for many thermal neutron-scattering studies, while μSR covers 10^7 to 10^{10} Hz for observable fluctuating phenomena. This difference in time scale explain the discrepancy in the magnetic ordering temperatures of LSCZO, 30 K for neutron scattering and 5 K for μSR. This picture is consistent with the view that the magnetic signals is quasielastic rather than truly elastic so that the temperature dependence of the intensity depends on the energy window as shown in LSCO with $x = 0.02$ (Fig. 3(b)). This *window* dependence is not observed in $\mathrm{La_2CuO_{4+y}}$, though very slow critical divergence with temperature may cause such dependence even in the coherent pinning case. Kimura *et al.* [19] have pointed out that doping Zn to LSCO with $x \sim 0.12$ considerably shortens the magnetic correlation length, 200 Å to 77 Å. This implies that the incoherent pinning can be destructive to the coherent pinning. On the other hand, the SDW order is most stable at $\delta \sim 1/8$ for LNSCO (LTT), which indicates that two different kinds of coherent pinning mechanisms are cooperative.

Let us assume that the characteristic frequency of AF fluctuations has spatial dependence around Zn, as schematically drawn in Fig. 4. Namely AF fluctuations are slowed down more drastically as closer to Zn and as temperature is lowered. Slightly below T_m determined from neutron scattering, the AF fluctuations near Zn can be detected by *elastic* neutron scattering, but not by μSR. Indeed, the intrinsic energy-width, i.e, the characteristic frequency, of the magnetic elastic peaks was estimated for LSCZO with $x = 0.14$ and $y = 0.012$, which is $\Gamma = 0.22$ meV ~ 0.05 THz. [17] At lower temperature, μSR starts detecting magnetic ordering from a region smaller than that for neutron scattering. In this model, the edge of the SDW domain is still substantially fluctuating, thus overlap of the domains may not necessarily result in percolation of magnetic coherence. Although it is not clear whether $\xi_{\mu\mathrm{SR}}$ calculated for *non-superconducting* region is the same for magnetic-ordering region in μSR time scale, these two entities are most likely correlated. Nevertheless, the model implies that there is a characteristic frequency of AF fluctuations for superconductivity, f_c: Superconductivity is suppressed in the region where AF fluctuations are slower than f_c. It is, however, not clear whether AF fluctuations with particular spatial modulation and frequency faster than f_c are necessary to or just compatible to high-T_c superconductivity.

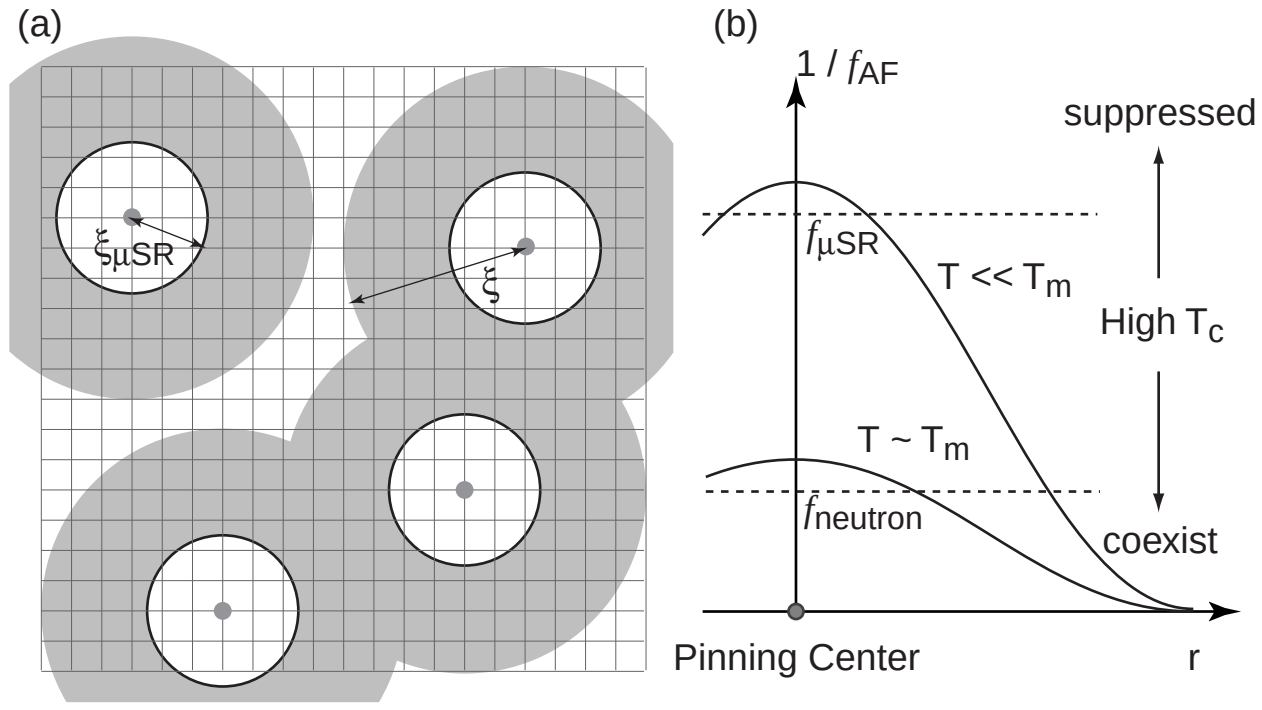

FIG. 4. (a) Schematic representation of quasistatic SDW domains around Zn ions for LSCZO with $y \sim 0.01$. $\xi \sim 23$ Å and $\xi_{\mu\mathrm{SR}} \sim 10$ Å are assumed for clarification. (b) Spatial dependence of the inverse of the characteristic AF fluctuations, $1/f_{AF}(r)$, around one of pinning centers, which are randomly distributed, at $T \leq T_m$ and $T \ll T_m$.

Systematic studies by combining probes with different time scales are clearly required to elucidate the nature of the *quasistatic* SDW ordering as well as the role of Zn doping in magnetism and superconductivity.

ACKNOWLEDGMENTS

The author gratefully acknowledges R.J. Birgeneau, Y. Endoh, M. Fujita, H. Hiraka, M.A. Kastner, H. Kimura, Y.S. Lee, G. Shirane, S. Wakimoto, and K. Yamada for international collaborative works on neutron scattering of the elastic magnetic peaks in LSCO and related compounds. The author would like to thank Y. Koike and J.M. Tranquada for invaluable discussions of their results.

---

[1] M.A. Kastner, R.J. Birgeneau, G. Shirane, and Y. Endoh, Rev. Mod. Phys. **70** (1998) 897 *and references therein.*

[2] D. Vaknin, S.K. Sinha, D.E. Moncton, D.C. Johnston, J.M. Newsom, C.R. Safenya and J.H.E. King, Phys. Rev. Lett. **58** (1987) 2802.

[3] B.J. Sternlieb, G.M. Luke, Y.J. Uemura, T.M. Riseman, J.H. Brewer, P.M. Gehring, K. Yamada, Y. Hidaka, T. Murakami, T.R. Thurston and R.J. Birgeneau, Phys. Rev. B **41** (1990) 8866.

[4] B. Keimer, N. Belk, R.J. Birgeneau, A. Cassanho, C.Y. Chen, M.Greven, M.A. Kastner, A. Aharony, Y. Endoh, R.W. Erwin and G. Shirane, Phys. Rev. B **46** (1992) 14034.

[5] H. Takagi, R.J. Cava, M. Marezio, B. Batlogg, J.J. Krajewski, W.F. Peck Jr., P. Bordet and D.E. Cox, Phys. Rev. Lett. **68** (1992) 3777.

[6] T. Nagao, Y. Tomioka, Y. Nakayama, K. Kishino and K. Kitazawa, Phys. Rev. B **48** (1993) 9689.

[7] S.-W. Cheong, G. Aeppli, T.E. Mason, H. Mook, S.M. Hayden, P.C. Canfield, Z. Fisk, K.N. Clausen and J.L. Maritinez, Phys. Rev. Lett. **67** (1991) 1791.

[8] K. Yamada, C.H. Lee, K. Kurahashi, J. Wada, S. Wakimoto, S. Ueki, H. Kimura, Y. Endoh, S. Hosoya, G. Shirane, R.J. Birgeneau, M. Greven, M.A. Kastner and Y.J. Kim, Phys. Rev. B **57** (1998) 6165.

[9] N. Bulut, D. Hone, D.J. Scalapino and N.E. Bickers, Phys. Rev. Lett. **64** (1990) 2723.

[10] T. Tanamoto, H. Kohno and H. Fukuyama, J. Phys. Soc. Japan **63** (1994) 2739.

[11] J.M. Tranquada, B.J. Sternlieb, J.D. Axe, Y. Nakamura and S. Uchida, Nature **375**, 561 (1995); J.M. Tranquada, J.D. Axe, N. Ichikawa, Y. Nakamura, S. Uchida and B. Nachumi, Phys. Rev. B **54** (1996) 7489; J.M. Tranquada, J.D. Axe, N. Ichikawa, A.R. Moodenbaugh, Y. Nakamura and S. Uchida, Phys. Rev. Lett. **78** (1997) 338; J.M. Tranquada, N. Ichikawa and S. Uchida, Phys. Rev. B **59** (1999) 14712.

[12] V.J. Emery, S.A. Kivelson and O. Zachar, Phys. Rev. B **56** (1997) 6120; S.A. Kivelson, E. Frandkin and V.J. Emery, Nature **393** (1998) 550.

[13] A. R. Moodenbaugh *et al.*, Phys. Rev. B **38** (1988) 4596.

[14] J.D. Axe and M.K. Crawford, J. Low Temp. Phys. **95** (1994) 271.

[15] T. Goto, S. Kazama, K. Miyagawa and T. Fukase, J. Phys. Soc. Japan **63** (1994) 3494.

[16] K. Kumagai, K. Kawano, I. Watanabe, K. Nishiyama and K. Nagamine, J. Supercond. **7** (1994) 63.

[17] K. Hirota, K. Yamada, I. Tanaka and H. Kojima, Physica B, **241-243** (1998) 817.

[18] T. Suzuki, T. Goto, K. Chiba, T. Shinoda, T. Fukase, H. Kimura, K. Yamada, M. Ohashi and Y. Yamaguchi, Phys. Rev. B **57** (1998) 3229.

[19] H. Kimura, K. Hirota, H. Matsushita, K. Yamada, Y. Endoh, S.H. Lee, C.F. Majkrzak, R.W. Erwin, G. Shirane, M. Greven, Y.S. Lee, M.A. Kastner and R.J. Birgeneau, Phys. Rev. B **59** (1999) 6517.

[20] H. Kimura, H. Matsushita, K. Hirota, Y. Endoh, K. Yamada, G. Shirane, Y.S. Lee, M.A. Kastner and R.J. Birgeneau, Phys. Rev. B **61** (2000) 14366.

[21] H. Matsushita, H. Kimura, M. Fujita, K. Yamada, K. Hirota and Y. Endoh, J. Phys. Chem. Solids **60** (1999) 1071.

[22] Y.S. Lee, R.J. Birgeneau, M.A. Kastner, Y. Endoh, S. Wakimoto, K. Yamada, R.W. Erwin, S.H. Lee and G. Shirane, Phys. Rev. B **60** (1999) 3643.

[23] S. Wakimoto, G. Shirane, Y. Endoh, K. Hirota, S. Ueki, K. Yamada, R.J. Birgeneau, M.A. Kastner, Y.S. Lee, P.M. Gehring and S.H. Lee, Phys. Rev. B **60** (1999) R769.

[24] S. Wakimoto, R.J. Birgeneau, M.A. Kastner, Y.S. Lee, R.W. Erwin, P.M. Gehring, S.H. Lee, M. Fujita, K. Yamada, Y. Endoh, K. Hirota and G. Shirane, Phys. Rev. B **61** (2000) 3699.

[25] S. Wakimoto, R.J. Birgeneau, Y.S. Lee and G. Shirane (unpublished).

[26] S. Wakimoto (private communication).

[27] M. Fujita, K. Yamada, H. Hiraka, S.H. Lee, P.M. Gehring, S. Wakimoto and G. Shirane (unpublished).

[28] M. Matsuda, R.J. Birgeneau, P. Böni, Y. Endoh, M. Greven, M.A. Kastner, S.H. Lee, Y.S. Lee, G. Shirane, S. Wakimoto and K. Yamada, Phys. Rev. B **61** (2000) 4326.

[29] M. Matsuda, M. Fujita, K. Yamada, R.J. Birgeneau, M.A. Kastner, H. Hiraka, Y. Endoh, S. Wakimoto and G. Shirane, Phys. Rev. B (2000) Ocober 1.

[30] H. Kimura, K. Hirota, M. Aoyama, T. Adachi, T. Kawamata, Y. Koike, K. Yamada and Y. Endoh, *Proceedings for ASR2000*

[31] B. Nachumi, A. Keren, K. Kojima, M. Larkin, G.M. Luke, J. Merrin, O. Tchernyshöv, Y.J. Uemura, N. Ichikawa, M. Goto and S. Uchida, Phys. Rev. Lett. **77** (1996) 5421.

TABLE I. Fundamental properties of elastic magnetic peaks of $\mathrm{La}_{2-x}\mathrm{Sr}_x\mathrm{Cu}_{1-y}\mathrm{Zn}_y\mathrm{O}_4$, $\mathrm{La}_{1.6}\mathrm{Nd}_{0.4}\mathrm{Sr}_x\mathrm{CuO}_4$ and $\mathrm{La}_2\mathrm{CuO}_{4+y}$. T_c is the onset temperature of superconductivity, T_m is the temperature the elastic magnetic peaks appear, ξ is the correlation length in the CuO_2 plane estimated from fits to the peak profile with the resolution, and μ is the magnetic moments of the elastic component. The peak position is described in a polar coordinate, namely, the incommensurability δ, defined as the distance between the magnetic peaks and the $(\frac{1}{2}\ \frac{1}{2}\ 0)$ position in the high temperature tetragonal lattice unit, and θ_Y, defined as the rotation of the incommensurate magnetic peaks (Y shift) with respect to the tetragonal [1 0 0]/[0 1 0] direction.

Sample	T_c (K)	T_m (K)	ξ (Å)	δ (r.l.u.)	μ (μ_B)	θ_Y (°)	Ref.
$\mathrm{La}_{2-x}\mathrm{Sr}_x\mathrm{Cu}_{1-y}\mathrm{Zn}_y\mathrm{O}_4$							
$x = 0.0$	0	325	> 600	0	0.55		[2]
$x = 0.02$	0	40	160^a, 25^b, 5^c	–	0.3	45	[28]
$x = 0.024$	0	25	95^a, 40^b, 3^c	0.016	–	45	[29]
$x = 0.03$	0	19	33	0.026	0.18	45	[25,26]
$x = 0.04$	0	17	37	0.037	0.15	45	[24,25,27]
$x = 0.05$	0	15	33^a, 25^b	0.045	0.13	45	[24,25]
$x = 0.053$	< 2	14	32	0.045	–	45	[27]
$x = 0.056$	6	13	39^D	0.051	–	45	[27]
			31^P	0.049		~ 0	
$x = 0.06$	12	11	26^D	0.053	0.06	45	[27,25]
			20^P	0.049		~ 0	
$x = 0.07$	17	11	27	0.069	0.05	~ 0	[27,25]
$x = 0.10$	28	19	70	0.11	–	–	[21]
$x = 0.12$	32	32	> 200	0.118	0.15	3.0	[19,20]
$x = 0.12$, $y = 0.03$	< 5	17	77	0.117	–	2.6	[19]
$x = 0.13$	36	19	88	0.12	–	–	[21]
$x = 0.14$, $y = 0.012$	19	20	80	0.132	–	–	[17]
$x = 0.15$	37	0					[8]
$x = 0.18$	35	0					[8]
$x = 0.21$, $y = 0.01$	< 2	20	70	0.135	–	2.1	[20]
$\mathrm{La}_{1.6-x}\mathrm{Nd}_{0.4}\mathrm{Sr}_x\mathrm{CuO}_4$							
$x = 0.12$	4	50	> 170	0.118	0.10	0^*	[11]
$x = 0.15$	11	45	–	0.130	–	–	[11]
$x = 0.20$	15	20	–	0.143	–	–	[11]
$\mathrm{La}_2\mathrm{CuO}_{4+y}$							
$y = 0.12$	40.5	40.5	> 400	0.121	0.15	3.3	[22]

(a),(b) and (c) denote correlation lengths along the orthorhombic a, b and c axes.

(D) and (P) denote "Diagonal" and "Parallel" modulations.

(*) No shift in the k direction was found for the charge-ordering peak at (2.24 0 0).